

Article

WS₂ Nanorod as a Remarkable Acetone Sensor for Monitoring Work/Public Places

Rajneesh Kumar Mishra ¹, Vipin Kumar ¹, Le Gia Trung ¹, Gyu Jin Choi ¹, Jeong Won Ryu ¹, Sagar M. Mane ², Jae Cheol Shin ^{2,*}, Pushpendra Kumar ³, Seung Hee Lee ^{4,5} and Jin Seog Gwag ^{1,*}

¹ Department of Physics, Yeungnam University, Gyeongsan 38541, Korea

² Division of Electronics and Electrical Engineering, Seoul Campus, Dongguk University, Seoul 04620, Korea

³ Department of Physics, Manipal University Jaipur, Jaipur 303007, India

⁴ Department of Nanoconvergence Engineering, Jeonbuk National University, Jeonju 54896, Korea

⁵ Department of Polymer Nano-Science and Technology, Jeonbuk National University, Jeonju 54896, Korea

* Correspondence: jcsin@dgu.ac.kr (J.C.S.); sweat3000@ynu.ac.kr (J.S.G.)

Abstract: Here, we report the synthesis of the WS₂ nanorods (NRs) using an eco-friendly and facile hydrothermal method for an acetone-sensing application. This study explores the acetone gas-sensing characteristics of the WS₂ nanorod sensor for 5, 10, and 15 ppm concentrations at 25 °C, 50 °C, 75 °C, and 100 °C. The WS₂ nanorod sensor shows the highest sensitivity of 94.5% at 100 °C for the 15 ppm acetone concentration. The WS₂ nanorod sensor also reveals the outstanding selectivity of acetone compared to other gases, such as ammonia, ethanol, acetaldehyde, methanol, and xylene at 100 °C with a 15 ppm concentration. The estimated selectivity coefficient indicates that the selectivity of the WS₂ nanorod acetone sensor is 7.1, 4.5, 3.7, 2.9, and 2.0 times higher than xylene, acetaldehyde, ammonia, methanol, and ethanol, respectively. In addition, the WS₂ nanorod sensor also divulges remarkable stability of 98.5% during the 20 days of study. Therefore, it is concluded that the WS₂ nanorod can be an excellent nanomaterial for developing acetone sensors for monitoring work/public places.

Keywords: WS₂ nanorods; gas sensors; acetone sensing; selective nature; durability; acetone sensing mechanism

Citation: Mishra, R.K.; Kumar, V.; Trung, L.G.; Choi, G.J.; Ryu, J.W.; Mane, S.M.; Shin, J.C.; Kumar, P.; Lee, S.H.; Gwag, J.S. WS₂ Nanorod as a Remarkable Acetone Sensor for Monitoring Work/Public Places. *Sensors* **2022**, *22*, 8609. <https://doi.org/10.3390/s22228609>

Academic Editor:

Manuel Alexandre

Received: 16 October 2022

Accepted: 4 November 2022

Published: 8 November 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

The rapidly increasing industrial evolutions in the fields of agriculture, automobiles, biomedical, and food packaging have introduced significant concerns about environmental monitoring technologies, leading to the development of reliable and durable gas sensors [1]. The human exhaled breath contains numerous types of gases, such as ketones, nitric oxide, aldehydes, volatile organic compounds, acids, and hydrogen sulfide [2,3]. Therefore, exhaled human breath is a significant and rousing issue from the outlook of biomedical applications to inspect different diseases. Interestingly, the exhaled human breath contains nearly 870 volatile organic compound types, indicating exclusive evidence regarding metabolic disorders [4]. Therefore, studying exhaled human breath can provide insights into crucial results of humans' normal or abnormal metabolic states arising from psychological stress [5]. Acetone molecules have been considered hazardous to human health and the environment. Acetone is a member of a family of volatile organic compounds that can influence the human nervous system and other organs under excessive exposure to concentrations of nearly 173 ppm [6]. Acetone is a vital aspect of the human metabolic system and can be examined through blood, breath, and urine [7,8]. It has been found to be a precise biomarker to recognize individuals with diabetes type-I due to the presence of high acetone vapor in the exhaled breath compared to healthy humans [9]. Various sensors, such as electrochemical, colorimetric, and resistive chemical

gas, have been studied to detect acetone [10–12]. The colorimetric sensor provides low accuracy and requires additional setups such as airbags and pumps, which makes it very expensive [11]. However, the resistive chemical gas sensor offers high sensitivity, stability, fast responses, portability, and recovery, which makes it a cheap gas-sensing setup with low-cost sensor fabrication [12].

Among various transition metal dichalcogenides (TMDs), tungsten disulfide (WS_2) is considered the most prominent two-dimensional (2D) nanomaterial for developing novel applications [13]. 2D layered nanomaterials have been extensively examined because of their remarkable properties, such as physical, optical, electronic, and mechanical, which can stimulate their performance in various applications [14]. WS_2 , a member of the layered hexagonal family, is a promising nanomaterial with 0.62 nm interlayer spacing composed of covalently bonded S-W-S atoms, where each layer is weakly bonded by Van der Waals forces [15,16]. WS_2 has no dangling bonds, which makes it extremely stable and non-reactive. It can absorb nearly 10% of the incident light due to its high absorption coefficient of $1.5 \times 10^6 \text{ cm}^{-1}$ [17]. It offers the desired engineering in the optical bandgap with high photoluminescence yields due to quantum confinements [18]. Interestingly, it exhibits an exclusive property of an engineering optical bandgap from an indirect optical bandgap of 1.4 eV (bulk) to a direct optical bandgap of 2.1 eV (monolayer), which provides a spin-orbit solid interaction [18,19]. Therefore, the WS_2 nanostructure has been studied in numerous types of applications, such as monolayer-based field-effect transistors [20], solar cells [21], monolayer-based light-emitting diodes [22], gas sensors [23], neuromorphic devices [24], biosensors [25], supercapacitors [26], lithium-ion batteries [27], and electrocatalytic [28] and photocatalytic water splitting [29]. WS_2 has been prepared using various methods, such as hydrothermal [30], solvothermal [31], chemical vapor deposition (CVD) [32], hot injection [33], thermal evaporation [34], and DC sputtering [35]. WS_2 has been explored in various types of morphologies, such as quantum dots [36], heterostructures [37], nanowire-nanoflake [38], nanorods [39], nanoflowers [40], and nanosheets [41].

Recently, various morphologies of WS_2 have been investigated for the detection of different types of gas. Liu et al. discussed the acetone gas-sensing behavior of WS_2/WO_3 heterojunctions [42]. The WS_2/WO_3 heterojunctions sensor offers reasonable sensitivity for acetone at a concentration of 20 ppm at 150 °C, selectivity in the presence of various hazardous gases, and stability for one month at a 150 °C working temperature for 20 ppm. Tang et al. inspected the NO_2 gas-sensing performance of the $WS_2/IGZO$ p-n heterojunction sensor [23]. It shows a response of 230% for 5 ppm NO_2 gas and 18,170% for 300 ppm NO_2 gas. It also suggests that the recovery percentage increases with increasing the gas concentration. Kim et al. studied the WS_2 nanosheet-based carbon monoxide gas sensor [43]. It depicts the CO response of 3 for 50 ppm concentration and the selective response of 3.75 for 50 ppm CO. It shows the response time of 339 s and recovery time of 567 s for 50 ppm CO. Ahmadvand et al. reported the ethanol sensor using the hybrid structure of the WS_2 and graphene oxide nanoribbons ($WS_2/GONRs$) [44]. It is observed that the $WS_2/GONRs$ show responses of 13.5 for 1 ppm and 438.5 for 21 ppm concentrations of ethanol at room temperature. Guang et al. explored ammonia sensing characteristics using the Au-coated WS_2 [45]. It shows a good gas response of 452% for 10 ppm of ammonia at room temperature. It also proposes a response time of 96 and a recovery time of 76 at room temperature for 10 ppm ammonia. Asres et al. investigated the H_2S sensing properties using the WS_2 sensor [46]. It shows that the WS_2 sensor behaves as a robust gas sensor for a high H_2S response. However, very limited reports exist for acetone sensing using the WS_2 sensing elements. Therefore, it is concluded that acetone detection using WS_2 sensors needs more attention from researchers to develop an extremely selective, responsive, and long-life gas sensor.

In this study, the WS_2 nanorods were prepared using the hydrothermal method for the acetone-sensing application. The WS_2 nanorod sensor displays outstanding acetone-sensing properties for 15 ppm concentrations at an operating temperature of 100 °C. It is observed that the WS_2 nanorod sensor shows a rapid response and fast recovery time.

Furthermore, the WS₂ nanorod sensor displays excellent acetone selectivity compared to other test gases. Moreover, the WS₂ nanorod sensor reveals outstanding stability during its long-term use. Therefore, it is concluded that these unique properties make it a remarkable acetone sensor for future applications in work/public places.

2. Materials and Methods

2.1. Materials Synthesis

The tungsten(IV) chloride, thioacetamide, ethanol, polyvinylidene fluoride (PVDF), hexamethyldisilazane (HMDS), xylene, methanol, N-Methyl-2-pyrrolidone (NMP), ammonia, and acetaldehyde were purchased from Sigma-Aldrich (St. Louis, MO, USA), which were utilized for the synthesis of WS₂ nanorods as received.

The WS₂ nanorods were prepared using a facile and eco-friendly hydrothermal process. In the synthesis process, 0.1904 g of the tungsten(IV) chloride compound was mixed in 80 mL of deionized (DI) water under dynamic stirring to achieve a good mixture. After that, 0.1803 g of thioacetamide was put into the prepared mixture solution using magnetic stirring to prepare a well-mixed solution. Furthermore, we added 1 mL of hexamethyldisilazane (HMDS) as a surfactant to control the morphology of the desired final product. Moreover, this prepared solution of tungsten(IV) chloride and thioacetamide was transferred to the 100 mL Teflon-lined autoclave. Further, this solution-filled autoclave was put into an air oven at 180 °C for twenty-four hours. Finally, the as-prepared nanomaterials were rinsed with ethanol and DI water. Further, it was dried at 70 °C for 10 h in a vacuum oven and processed with heat treatment at 200 °C for 3 h under a vacuum.

2.2. Materials Characterizations

Transmission electron microscopy (TEM) (JEOL JEM 2100F, JEOL Ltd., Tokyo, Japan) was utilized to explore the structural, morphological, lattice spacings, and lattice planes of WS₂ nanorods. In addition, the atomic-resolution high-angle annular dark-field (HAADF) and electron energy loss spectroscopy (EELS) were investigated using a JEOL, JEM-2100F, JEOL Ltd., Tokyo, Japan, to study the elemental color mapping of WS₂ nanorods.

2.3. WS₂ NRs-Based Sensor Fabrication and Measurements

The following process was used to fabricate the WS₂ nanorods-based acetone sensor: The first binder solution of 0.5 g of polyvinylidene fluoride (PVDF) was prepared using solvent N-Methyl-2-pyrrolidone (NMP) in a drop-wise manner. After that, we slowly added WS₂ nanorod powder to the binder solution and mixed it well to obtain the desired solution for sensor fabrication. The WS₂ nanorod gluey solution was coated on the glass substrate using drop-casting and dried slowly at 40 °C. Further, the silver paste was used to make contact on both sides of the film (deposited on glass) for the electrical connection. The gas-sensing measurements were conducted using the Keithley-2100 multimeter; however, the Motwane-454 multimeter was used to maintain the temperature inside the test chamber. The acetone gas-sensing measurements were investigated at 25 °C–100 °C for 5 ppm, 10 ppm, and 15 ppm concentrations. The acetone concentrations were injected into the test gas chamber using a Hamilton micro-syringe. In addition, the volume of the acetone concentrations (*C*, ppm) was estimated using Equation (1) [47]:

$$C \text{ (ppm)} = \frac{22.4 \times T \times V_l \times \rho}{V \times M} \times 1000 \quad (1)$$

where *C* (ppm) is the desired acetone concentration, ρ (g L⁻¹) is the liquid acetone density, *V_l* (μL) is the volume of the liquid acetone, *M* (g mol⁻¹) is the molecular weight of the acetone, *T* (°C) is the working temperature of acetone sensing, and *V* is the acetone gas test chamber.

3. Results and Discussion

3.1. Morphological, Structural, and Elemental Study

Figure 1 shows the schematic depiction of synthesis, the crystal structure, and the acetone-sensing properties of the WS₂ nanorods. It depicts the solution preparation of tungsten and thioacetamide with the HMDS surfactant. It also reveals the hydrothermal reaction conditions at 180 °C for 24 h. Furthermore, it verifies the successful synthesis of WS₂ nanorods via TEM images. It shows the crystallographic illustration of the WS₂ crystal structure and the visualization of the acetone-sensing mechanism. The detailed synthesis procedure was discussed in the material synthesis section. The detailed synthesis procedure was discussed in the acetone-sensing mechanism section.

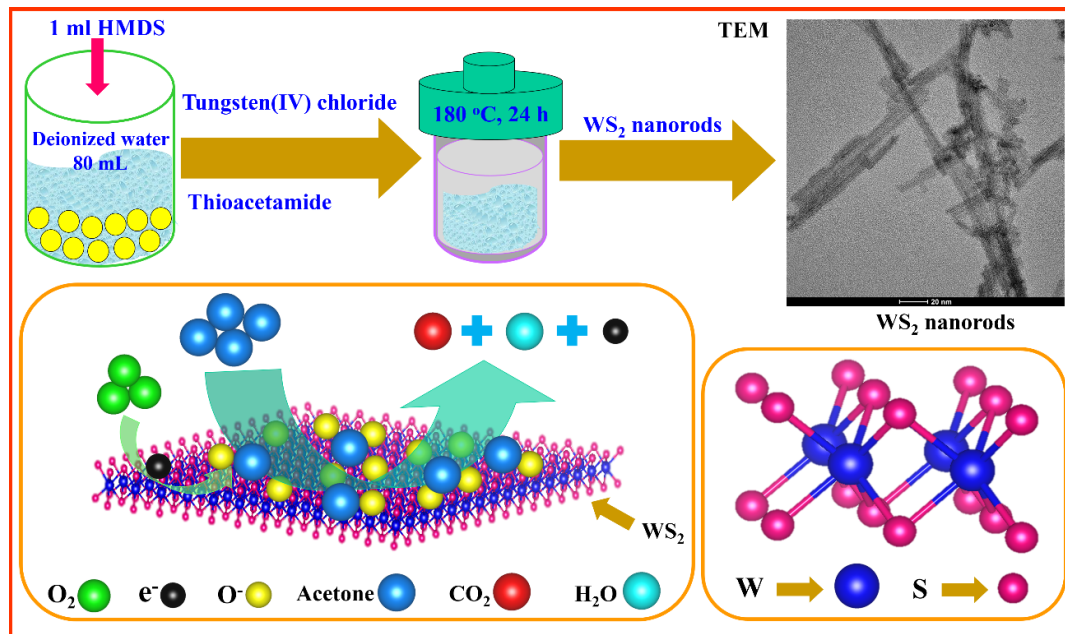


Figure 1. Concept of the WS₂ nanorod synthesis method. Crystallographic presentation of WS₂ crystal structure. Graphic of the acetone-sensing mechanism of the WS₂ sensor. Visualization and interactions of molecules and electrons during acetone sensing of WS₂ sensor.

Figure 2a–d display the morphology of the WS₂ nanorods using the TEM at different scale bars. Figure 2a,b depict the agglomerations of the WS₂ nanorods with various sizes and lengths. It seems to be overlapped, crossed WS₂ nanorods, which can improve oxygen molecules' conduction mechanism and interactions with the nanorods and gas-sensing properties. Figure 2c displays the WS₂ nanorods whose length varies from nearly 20 nm to 200 nm. It also elucidates the WS₂ nanorods whose widths fluctuate from 3 nm to 6 nm. Figure 2d shows several attached WS₂ nanorods, forming various intersections between nanorods. It also reveals a thickness of 3 nm to 6 nm and a length of 20 nm to 200 nm of WS₂ nanorods. It seems to develop several solid connections/attachments between the nanorods, which offer a large surface area, more adsorption, and chemisorption of atmospheric oxygen and gas molecules.

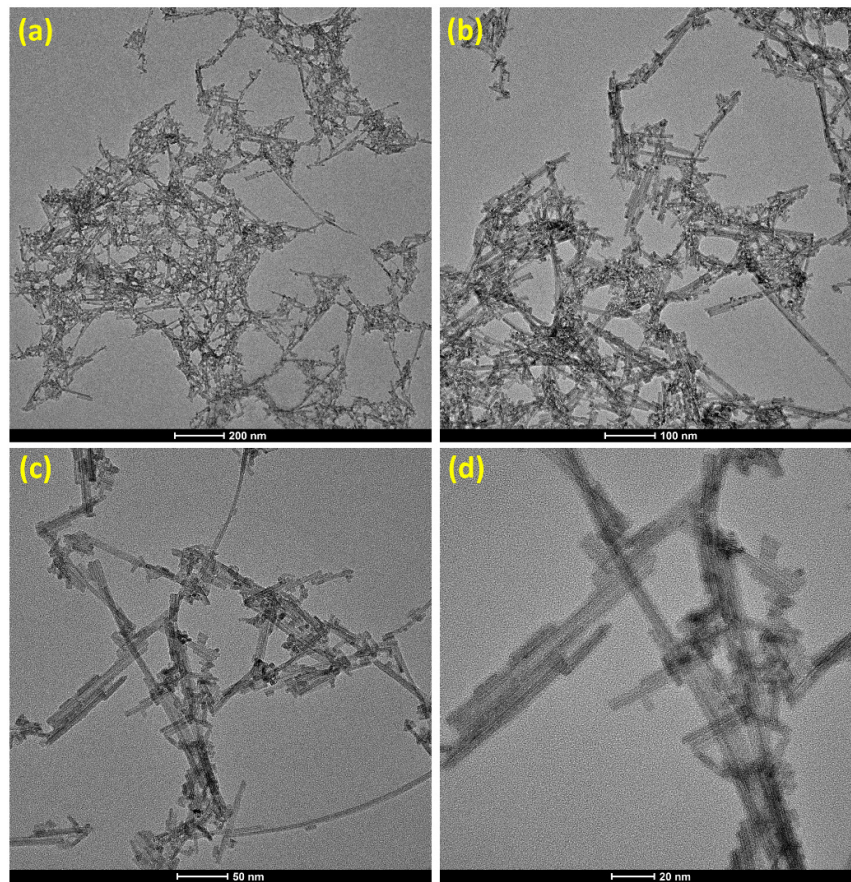


Figure 2. (a–d) TEM images of the WS₂ nanorods at the different scales.

Figure 3a–e show the HRTEM and fast Fourier transform (FFT) patterns to explore the crystal structure, lattice spacing, and lattice planes of the WS₂ nanorods. Figure 3a displays the HRTEM image of the WS₂ nanorods with 2 to 5 nm thickness, and the length varies from 20 nm to 100 nm. Figure 3b,c reveal the magnified HRTEM images of the WS₂ nanorods, indicating lattice spacings of 0.28 nm corresponding to the (100) lattice plane. Further, Figure 3d,e exhibit the FFT patterns of the WS₂ nanorods to study the lattice plane and spacing, signifying the growth of the (100) lattice plane corresponding to the lattice spacing of 0.28 nm. The FFT pattern justifies the lattice spacing results, as shown in Figure 3a. The literature reports discussed similar HRTEM and FFT results of WS₂ nanostructures [48,49].

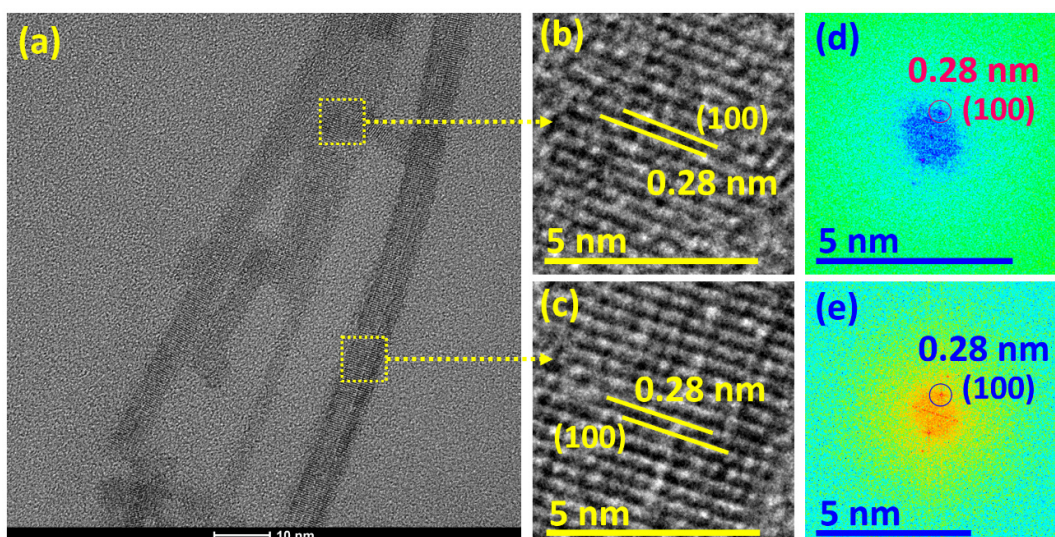


Figure 3. (a) HRTEM image, (b,c) magnified HRTEM images, and corresponding (d,e) FFT patterns of the WS₂ nanorods.

In addition, the elemental information of the WS₂ nanorods was studied using the HAADF image consistent with the color mapping of tungsten and sulfur elements. Figure 4a–c unveil the dark-field TEM (HAADF) image and corresponding elemental mapping of tungsten and sulfur elements of the WS₂ nanorods. Figure 4a divulges the HAADF image of the WS₂ nanorods to examine the elements' composition and presence in the desired area. It also shows short to long WS₂ nanorods with thin diameters. Figure 4b,c reveal the color mapping of tungsten and sulfur elements of the WS₂ nanorods from the selected area (as shown in Figure 4a). It exhibits the presence of tungsten and sulfur elements over the selected area, confirming the successful formation of the WS₂ composition. These results are well-matched and supported by the HRTEM and FFT results of the WS₂.

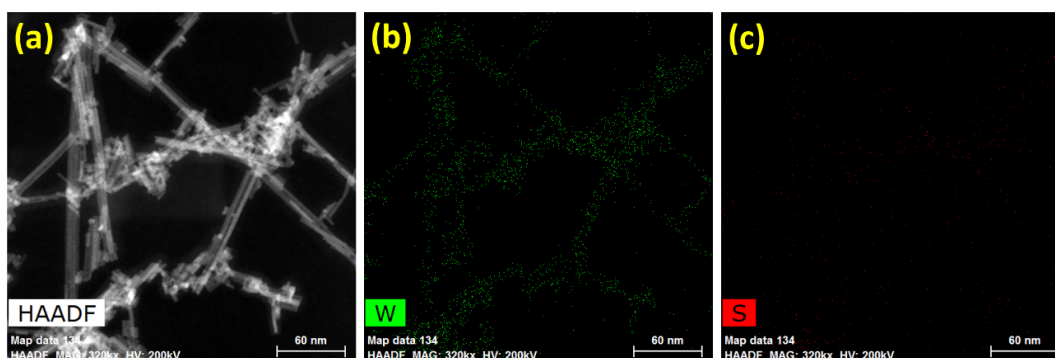


Figure 4. (a) HAADF image and corresponding color mapping of (b) tungsten and (c) sulfur elements of the WS₂ nanorods.

3.2. Acetone-Sensing Characteristics

The temperature and test gas concentration mainly affect the gas-sensing properties of the sensor. Therefore, it is necessary to find the optimum working temperature for a specific gas concentration of the chemical gas sensors. In light of this, we investigated the acetone-sensing properties of the WS₂ nanorod sensor at 25 °C–100 °C for 5 ppm, 10 ppm, and 15 ppm concentrations. The desired acetone concentration of the WS₂ nanorod sensor was evaluated with the help of Equation (1). In addition, the acetone gas sensitivity [S (%)] of the WS₂ nanorod sensor was estimated using Equation (2) [50]:

$$S(\%) = \frac{R_a - R_{acetone}}{R_a} \times 100 \quad (2)$$

where R_a and $R_{acetone}$ are the resistances measured under air and different acetone gas concentrations at different operating temperatures.

Figure 5a shows the sensitivity vs. temperature plots of the WS₂ nanorod sensor for 5, 10, and 15 ppm acetone concentrations. It is found that the sensitivity increases with the increasing acetone concentration and operating temperature of the WS₂ nanorod sensor. The WS₂ nanorod sensor shows the highest sensitivity of 94.5% for 15 ppm of acetone at 100 °C. However, the WS₂ nanorod sensor reveals the lowest sensitivity of 18.5% for 5 ppm of acetone at 25 °C. The high sensitivity observed at 100 °C compared to the low sensitivity at 25 °C, 50 °C, and 75 °C for increasing concentrations may be attributable to the following reasons: (i) The high thermal energy at 100 °C (as compared to 25 °C) allows more thermally excited electrons to reach the conduction band, which can easily interact with the oxygen molecules to form the active site on the WS₂ nanorod sensor surface; (ii) the large surface area of the 2D WS₂ nanorod provides more interactions of oxygen molecules to form a large amount of active site on the sensor surface; (iii) the high electronic/ionic conductivity of WS₂; (iv) high electronic and chemical responsiveness; and (v) rapid adsorption/desorption and extremely high diffusion of acetone molecules, leading to fast and outstanding sensitivity [51–53]. Figure 5b manifests the sensitivity vs. acetone concentration plots of the WS₂ nanorod sensor at two operating temperatures of 25 °C and 100 °C. It is perceived that the WS₂ nanorod sensor divulges low sensitivities of 18.5%, 24.7%, and 32.5% at an operating temperature of 25 °C for 5, 10, and 15 ppm of acetone, respectively. However, the WS₂ nanorod sensor displays high sensitivities of 64.5%, 82.4%, and 94.5% at an operating temperature of 100 °C for 5, 10, and 15 ppm of acetone, respectively. It is also elucidated that the sensitivity increases with the acetone concentration at 25 °C and 100 °C. Many factors influence the sensitivity of the WS₂ nanorod sensor due to the following reasons: (i) The high diffusion rate of gas molecules on the WS₂ nanorod sensor surface due to the high concentration gradient of acetone molecules. The concentration gradient is proportional to the diffusion rate; therefore, acetone sensitivity increases with the acetone concentration at 25 °C and 100 °C. Furthermore, (ii) the acetone molecules formed a significant dipole moment due to the presence of the C-C=O group. It encourages the chemical adsorption/desorption and redox reaction capability of the WS₂ nanorod sensor material [3,54].

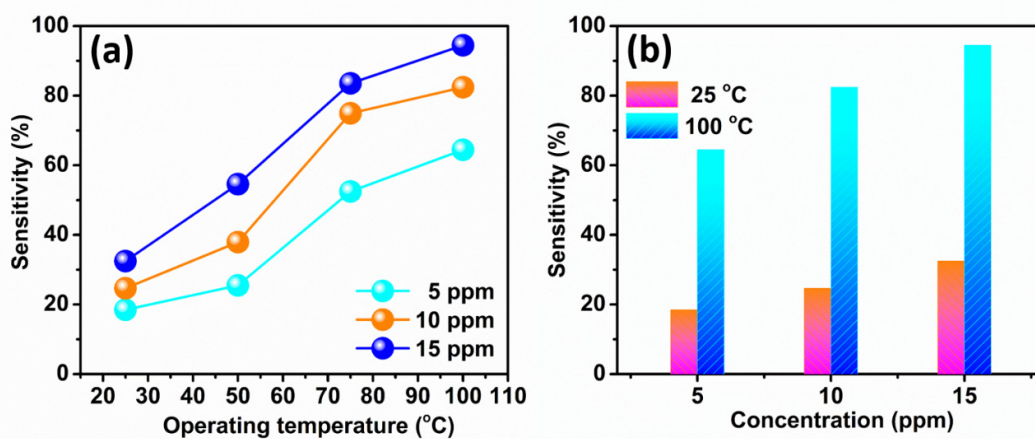


Figure 5. (a) Acetone sensitivity vs. temperature plots and (b) acetone sensitivity vs. concentration plots of the WS₂ nanorod sensor.

Figure 6a shows the transient characteristic of the WS₂ nanorod sensor at 25 °C and 100 °C for 5, 10, and 15 ppm of acetone. It shows a fast response and recovery at all acetone

concentrations. It also exhibits that as the acetone concentration increases, the recovery and the response time decrease. This may be because of the enhanced chemisorption rate of acetone molecules on the WS₂ nanorod sensor's surface [55,56]. Figure 6b illustrates the response and recovery time plot of acetone molecules of the WS₂ nanorod sensor. The response and recovery times were estimated when the WS₂ nanorod sensor attained 90% of its maximum value and recovered 90% of its minimum value [57]. The WS₂ nanorod sensor displays a quick response time of 3.02 min and a recovery time of 3.41 min at 100 °C for the 15 ppm concentration. This may be due to the high surface area of WS₂ nanorods, rapid adsorption/desorption, and the chemisorption process. On the other hand, the reduction in the depletion layer and potential barrier height is due to more thermally excited electrons in the conduction band, leading to quick response and recovery [58,59].

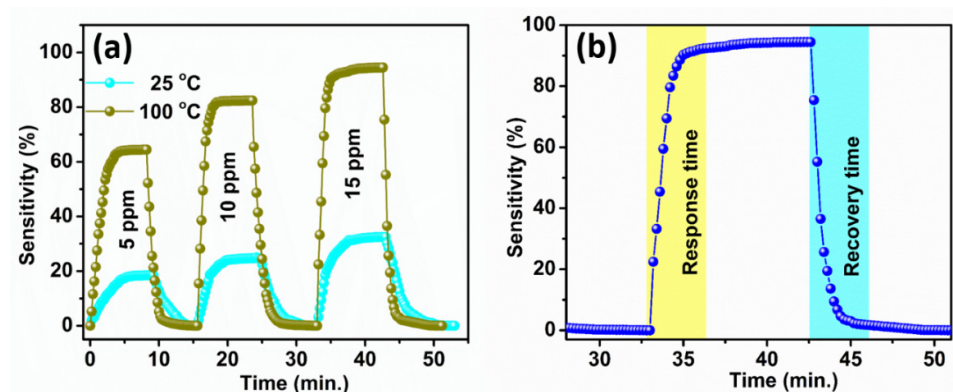


Figure 6. The WS₂ nanorod sensor: (a) Transient characteristics at 25 °C and 100 °C for 5, 10, and 15 ppm acetone concentrations and (b) estimation of response and recovery time at 100 °C for 15 ppm of acetone.

Interestingly, the selectivity of the gas sensor plays a vital role in distinguishing the specific gas from various other gases. Here we investigated the selectivity of the WS₂ nanorod sensor to six gases, including acetone. Figure 7a shows the sensitivity vs. test gas plots of the WS₂ nanorod sensor at 100 °C for 15 ppm concentrations of various gas to disclose the selectivity behavior. It is detected that the WS₂ nanorod sensor reveals the maximum sensitivity to acetone (94.5%) compared to the other gas, such as ethanol (46.4%), methanol (33.2%), ammonia (25.7%), acetaldehyde (21.2%), and xylene (13.2%) at 100 °C for 15 ppm concentrations. In addition, the selectivity coefficient (C_s) to quantify the sensitivity of the WS₂ nanorod sensor was calculated using the following Equation (3) [60].

$$C_s = \frac{S_{acetone}}{S_{other\ gas}} \quad (3)$$

The estimated values of C_s of the WS₂ nanorod-based acetone sensor are 2.0 (ethanol), 2.9 (methanol), 3.7 (ammonia), 4.5 (acetaldehyde), and 7.1 (xylene). These C_s values indicate that the sensitivity of the WS₂ nanorod sensor to acetone is 7.1, 4.5, 3.7, 2.9, and 2.0 times higher than xylene, acetaldehyde, ammonia, methanol, and ethanol, respectively. Therefore, it is concluded that the WS₂ nanorod sensor is most suitable for acetone detection compared to other tested gases at 100 °C with 15 ppm concentrations. The lowest unoccupied orbital energy has different values for different gases [61]. Figure 7b depicts the stability plot of the WS₂ nanorod sensor for 20 days for 15 ppm concentrations at 100 °C. The sensitivity of the WS₂ nanorod sensor slowly reduces with time from 94.5% (on the 1st day) to 93.0% (on the 20th day). It also exhibits the excellent stability of the WS₂ nanorod sensor of 98.5% over twenty days for a 15 ppm acetone concentration at 100 °C. The high stability of the WS₂ nanorod sensor may be due to the excellent electrical and thermal conductivity of WS₂. On the other hand, the nanorod's large surface area also provides high exposure to acetone molecules and rapid interactions with the adsorbed oxygen-active ions (O⁻), leading to excellent stability.




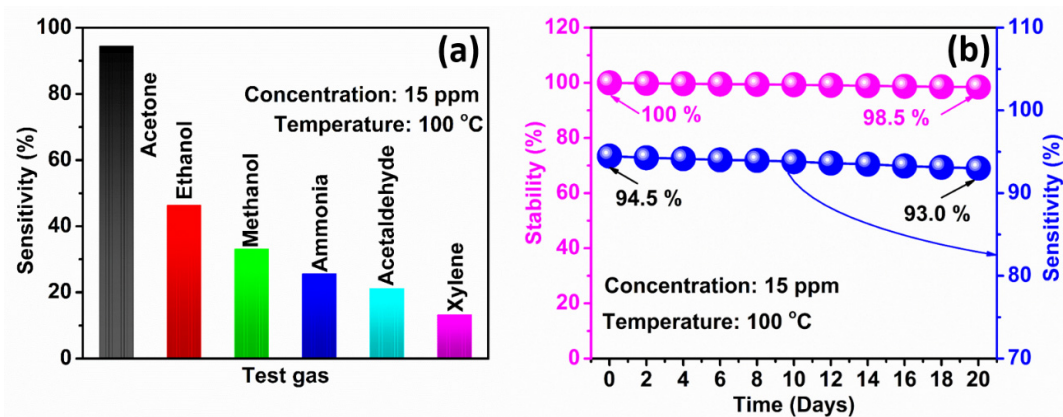


Figure 7. (a) Selectivity and (b) stability and corresponding sensitivity of the WS₂ nanorod sensor.

In addition, a comparison between the various TMD-based acetone sensors has been discussed here with our observed results of the WS₂ nanorod sensor. The MoS₂-CuO nanocomposite sensor exhibited a high response of 16.21 for 10 ppm acetone at room temperature. It also showed a fast response of 61 s and recovery of 85 s [62]. The WS₂/WO₃ sensor has demonstrated a prolonged response time of 823 s and recovery time of 1093 s at 100 °C for 20 ppm acetone [42]. The decoration of Co₃O₄ on ZnS nanorods has been discussed regarding the acetone-sensing characteristics, which elucidated a high response of 1650% for 500 ppm acetone at room temperature under 2.2 mW cm⁻² UV illumination [63]. A 2D SnS nanoflakes-based sensor displayed a high response of 1000%, a response time of ~35 s, and a recovery time of ~45 s at 100 °C for 10 ppm acetone [64]. SnS₂-based sensors have demonstrated a high response of ~25, a response time of ~210 s, and a recovery time of ~600 s at 300 °C for 10 ppm acetone [65]. We found very limited reports on the WS₂-based acetone sensor in the literature. Therefore, it is concluded that the WS₂ nanorods could be a promising nanomaterial for an acetone sensor.

3.3. Oxygen Active Site Formation and Acetone Molecule Detection Mechanism

The acetone recognition mechanism of the WS₂ nanorod sensor essentially depends on the change in sensor resistance during gas sensing. The chemisorption reaction among the adsorbed active sites (O⁻) on the WS₂ nanorod surface and acetone molecules determines the gas-sensing process [66]. It regulates the concentration of oxygen molecules with the WS₂ nanorod sensor surface and modulates the sensor resistance [67]. Equations (4)–(6) represent the interaction reactions of atmospheric oxygen molecules and the creation of active sites (O⁻) on the WS₂ nanorod surface at different operating temperatures [51,68,69].



These active oxygen ions/sites are responsible for interacting with the acetone molecules. Therefore, the possible reaction between the adsorbed active sites (O⁻) and acetone molecules on the WS₂ nanorod sensor surface is discussed in Equation (7) [59,70].




Figure 8a–f show the schematic drawings of the oxygen adsorption reaction, depletion layer formation, the creation of a potential barrier, and reaction mechanisms of acetone molecules with the oxygen active sites (O⁻) on the WS₂ nanorod surface. Figure 8a–c depict the schematic sketch of the creation of active sites on the WS₂ nanorod sensor surface and depletion region in the electronic band structure. Firstly, atmospheric oxygen

$[O_2(\text{atmospheric})]$ was adsorbed on the WS_2 nanorod sensor surface ($O_2(\text{adsorbed})$) using the process discussed in Equation (4). Further, it is expected that, below $100\text{ }^\circ\text{C}$, the adsorbed oxygen ($O_2(\text{adsorbed})$) interacts with the electrons in the conduction band and creates the active sites (O_2^-) on the WS_2 surface, as discussed in Equation (5). After that, active sites (O_2^-) take more thermally excited electrons from the conduction band of the WS_2 nanorod, finally creating the active sites (O^-) on the WS_2 nanorod sensor surface, as discussed in Equation (6). Figure 8b portrays a schematic view of the emergence of a depletion layer around the WS_2 nanorod sensor surface during the adsorption process, which plays an intensive role in acetone sensing. Figure 8c describes the electronic band structure of the WS_2 nanorod sensor following the various steps as discussed in Equations (4)–(6). It illustrates that the depletion layer and potential barrier are created during the adsorption and active site (O^-) formation on the WS_2 nanorod sensor. Similar reports have studied and discussed the exploration of the concept of the creation of active oxygen ions/sites in the literature [71–73]. Figure 8d reveals the graphical visualization of the interaction between acetone molecules and the active site (O^-) on the WS_2 nanorod sensor surface, following the process discussed in Equation (7), showing the liberation of CO_2 gas, H_2O , and electrons in the conduction band of the WS_2 nanorod. Figure 8e discloses an illustration of the acetone-sensing mechanism (as discussed in Equation (7)) on the WS_2 nanorod sensor surface and the release of carbon dioxide, water, and electrons. Figure 8f unveils the electronic band structure of the chemisorption of acetone molecules on the WS_2 nanorod sensor (as discussed in Equation (7)). It is observed that the declining depletion region and the height of the potential barrier are created during the adsorption and creation of the active site (O^-) on the WS_2 nanorod surface. It also frees electrons in the conduction band of the WS_2 nanorod sensor during the release of the carbon oxide and water molecules. The sensitivity of the acetone increases with increasing temperature and concentration due to the reduction in the depletion region and potential barrier heights, as schematically illustrated in Figure 8a–f, which supports the results discussed in Figures 5 and 6. Similar reports of acetone-sensing mechanisms have been studied and discussed in the literature [73–76].

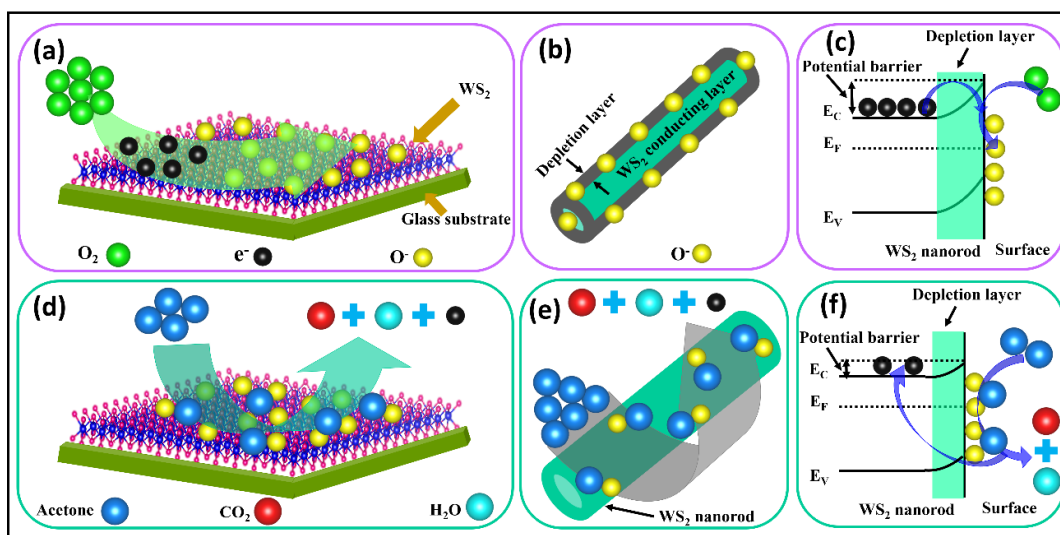


Figure 8. WS_2 nanorod sensor: (a,d) Graphical illustration of adsorption of oxygen via electron interactions, formation of the active sites on the surface, and interaction of active sites with the acetone molecules; (b,e) visualization of a depletion layer formation around the WS_2 nanorod by adsorbed active sites, and acetone-sensing reaction mechanism; (c,f) electronic band structure during active site formation and chemisorption of acetone molecules of the WS_2 nanorod sensor.

4. Conclusions

In conclusion, we studied an acetone gas-sensing application based on WS₂ nanorods (NRs). The WS₂ nanorod sensor shows the highest sensitivity of 94.5% at 100 °C for 15 ppm acetone. It also discloses the admirable selectivity of acetone compared to other gases, such as xylene, methanol, ammonia, acetaldehyde, and ethanol at 100 °C with a 15 ppm concentration. Further, it demonstrates fantastic stability over 20 days at 100 °C for a 15 ppm concentration. Consequently, it is concluded that the WS₂ nanorod can offer a new choice for fabricating reliable, low-cost, environmentally friendly acetone sensors for observing workplace safety.

Author Contributions: Conceptualization, R.K.M. and J.S.G.; methodology, R.K.M., V.K. and J.S.G.; software, G.J.C. and J.W.R.; validation, L.G.T. and P.K.; formal analysis, S.M.M. and P.K.; investigation, S.M.M., G.J.C. and J.W.R.; resources, J.S.G., S.H.L. and J.C.S.; data curation, S.M.M., G.J.C. and J.W.R.; writing—original draft preparation, R.K.M.; writing—review and editing, R.K.M., S.H.L. and J.S.G.; visualization, R.K.M. and V.K.; supervision, R.K.M., S.H.L., J.C.S. and J.S.G.; project administration, J.S.G.; funding acquisition, J.S.G. All authors have read and agreed to the published version of the manuscript.

Funding: This research was supported by a research grant from Yeungnam University (2021).

Acknowledgments: This research was supported by a research grant from Yeungnam University (2021).

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Fu, Q.; Lyu, P.; Handschuh-Wang, S.; Teng, L.; Zheng, B. Facile synthesis of hierarchical Co₃O₄/MWCNT composites with enhanced acetone sensing property. *Ceram. Int.* **2022**, *48*, 28419–28427.
2. Zhou, X.; Xue, Z.; Chen, X.; Huang, C.; Bai, W.; Lu, Z.; Wang, T. Nanomaterial-based gas sensors used for breath diagnosis. *J. Mater. Chem. B* **2020**, *8*, 3231–3248.
3. Lv, S.; Fan, J.; Liu, F.; Zhang, Y.; Jiang, L.; Ouyang, S.; Zhang, C.; Wang, C.; Sun, P.; Wang, L.; et al. YSZ-based mixed potential type acetone gas sensor attached with CuSb₂O₆ sensing electrode for ketosis diagnosis. *Sens. Actuators B* **2022**, *370*, 132408.
4. Costello, B.d.L.; Amann, A.; A.-Kateb, H.; Flynn, C.; Filipiak, W.; Khalid, T.; Osborne, D.; Ratcliffe, N.M. A review of the volatiles from the healthy human body. *J. Breath Res.* **2014**, *8*, 014001.
5. Tai, H.; Wang, S.; Duan, Z.; Jiang, Y. Evolution of breath analysis based on humidity and gas sensors: Potential and challenges. *Sens. Actuators B* **2020**, *318*, 128104.
6. Zhang, Z.; Wu, Y.; Du, H.; Sun, Y.; Sun, S.; Xu, S.; Cong, L.; Sun, P. Acetone sensing mechanism of Ar/O₂ plasma modified indium oxide electrospun fibers: A combined DFT and experimental study. *J. Alloys Compd.* **2022**, *895*, 162017.
7. Zhu, Z.; Li, Z.; Xiong, X.; Hu, X.; Wang, X.; Li, N.; Jin, T.; Chen, Y. ZnO/ZnSe heterojunction nanocomposites with oxygen vacancies for acetone sensing. *J. Alloys Compd.* **2022**, *906*, 164316.
8. Oh, S.; Park, J.-S.; Lee, H.-J.; Jeong, H.M.; Selective acetone gas sensing of Cu₂(OH)₃F/CuO enhanced by hydroxy bonds and fluorine substitution. *Sens. Actuators B* **2022**, *372*, 132662.
9. Atanasova, G.; Dilova, T.; Dikovska, A. Og.; Nikov, Ro. G.; Nedyalkov, N.N.; Acetone-sensing properties of ZnO-noble-metals composite nanostructures and their improvement by light irradiation. *Thin Solid Films* **2022**, *750*, 139198.
10. Sharma, T.S.K., Hwa, K.Y. Facile Synthesis of Ag/AgVO₃/N-rGO Hybrid Nanocomposites for electrochemical detection of levofloxacin for complex biological samples using screen-printed carbon paste electrodes. *Inorg. Chem.* **2021**, *60*, 6585–6599.
11. Wang, D.; Zhang, F.; Prabhakar, A.; Qin, X.; Forzani, E.S.; Tao, N. Colorimetric sensor for online accurate detection of breath acetone. *ACS Sens.* **2021**, *6*, 450–453.
12. Majhi, S.M.; Ali, A.; Greish, Y.E.; E.-Maghraby, H.F.; Qamhieh, N.N.; Hajamohideen, A.R.; Mahmoud, S.T. Accordion-like-Ti₃C₂ MXene-based gas sensors with sub-ppm level detection of acetone at room temperature. *ACS Appl. Electron. Mater.* **2022**, *4*, 4094–4103.
13. Huang, G.; Liu, H.; Wang, S.; Yang, X.; Liu, B.; Chen, H.; Xu, M. Hierarchical architecture of WS₂ nanosheets on graphene frameworks with enhanced electrochemical properties for lithium storage and hydrogen evolution. *J. Mater. Chem. A* **2015**, *3*, 24128–24138.
14. Chen, Y.; Sun, M. Two-dimensional WS₂/MoS₂ heterostructures: Properties and applications. *Nanoscale* **2021**, *13*, 5594–5619.
15. Miao, W.; Gai, X.; Zhao, F.; Wang, J. Excitation induced asymmetric fluorescence emission in 2D-WS₂ quantum dots. *Mater. Adv.* **2022**, *3*, 1772–1779.
16. Luo, X.; Huang, J.; Huang, Y.; Cao, L.; Li, J.; Wang, Y.; Xu, Z.; Wei, S.; Kajiyoshi, K. Self-templated induced carbon-supported hollow WS₂ composite structure for high-performance sodium storage. *J. Mater. Chem. A* **2021**, *9*, 21366–21378.

17. Villamayor, M.M.S.; Lindblad, A.; Johansson, F.O.L.; Tran, T.; Pham, N.H.; Primetzhofer, D.; Sorgenfrei, N.L.A.N.; Giangrisotomi, E.; Fohlich, A.; Lourenço, P.; et al. Growth of two-dimensional WS₂ thin films by reactive sputtering. *Vacuum* **2021**, *188*, 110205.
18. Das, R.; Bora, A.; Giri, P.K. Quantitative understanding of the ultra-sensitive and selective detection of dopamine using a graphene oxide/WS₂ quantum dot hybrid. *J. Mater. Chem. C* **2020**, *8*, 7935–7946.
19. Jo, S.; Ubrig, N.; Berger, H.; Kuzmenko, A.B.; Morpurgo, A.F. Mono- and bilayer WS₂ light-emitting transistors. *Nano Lett.* **2014**, *14*, 2019–2025.
20. Sebastian, A.; Pendurthi, R.; Choudhury, T.H.; Redwing, J.M.; Das, S. Benchmarking monolayer MoS₂ and WS₂ field-effect transistors. *Nat. Commun.* **2021**, *12*, 693.
21. Rafiq, M.K.S.B.; Amin, N.; Alharbi, H.F.; Luqman, M.; Ayob, A.; Alharthi, Y.S.; Alharthi, N.H.; Bais, B.; Akhtaruzzaman, M. WS₂: A new window layer material for solar cell application. *Sci. Rep.* **2020**, *10*, 771.
22. Sheng, Y.; Chen, T.; Lu, Y.; Chang, R.-J.; Sinha, S.; Warner, J.H. High-performance WS₂ monolayer light emitting tunneling devices using 2D materials grown by chemical vapor deposition. *ACS Nano* **2019**, *13*, 4530–4537.
23. Tang, H.; Li, Y.; Sokolovskij, R.; Sacco, L.; Zheng, H.; Ye, H.; Yu, H.; Fan, X.; Tian, H.; Ren, T.-L.; et al. Ultra-high sensitive NO₂ gas sensor based on tunable polarity transport in CVD-WS₂/IGZO p-N heterojunction. *ACS Appl. Mater. Interfaces* **2019**, *11*, 40850–40859.
24. Yan, X.; Zhao, Q.; Chen, A.P.; Zhao, J.; Zhou, Z.; Wang, J.; Wang, H.; Zhang, L.; Li, X.; Xiao, Z.; et al. Vacancy-induced synaptic behavior in 2D WS₂ nanosheet-based memristor for low-power neuromorphic computing. *Small* **2019**, *15*, 1901423.
25. Zuo, X.; Dai, H.; Zhang, H.; Liu, J.; Ma, S.; Chen, X. A peptide-WS₂ nanosheet based biosensing platform for determination of β -secretase and screening of its inhibitors. *Analyst* **2018**, *143*, 4585–4591.
26. Liu, S.; Zeng, Y.; Zhang, M.; Xie, S.; Tong, Y.; Cheng, F.; Lu, X. Binder-free WS₂ nanosheets with enhanced crystallinity as a stable negative electrode for flexible asymmetric supercapacitors. *J. Mater. Chem. A* **2017**, *5*, 21460–21466.
27. Yin, L.; P.-Cong, D.; Jeon, I.; Kim, J.-P.; Cho, J.; Jeong, S.-Y.; Lee, H.W.; Cho, C.-R. Electrochemical performance of vertically grown WS₂ layers on TiNb₂O₇ nanostructures for lithium-ion battery anodes. *Chem. Eng. J.* **2020**, *382*, 122800.
28. Wang, D.; Li, Q.; Han, C.; Xing, Z.; Yang, X. When NiO@Ni meets WS₂ nanosheet array: A highly efficient and ultrastable electrocatalyst for overall water splitting. *ACS Cent. Sci.* **2018**, *4*, 112–119.
29. Zhu, B.; Zhang, F.; Qiu, J.; Chen, X.; Zheng, K.; Guo, H.; Yu, J.; Bao, J. A novel Hf₂CO₂/WS₂ van der Waals heterostructure as a potential candidate for overall water splitting photocatalyst. *Mater. Sci. Semicond. Process.* **2021**, *133*, 105947.
30. Piao, M.; Chu, J.; Wang, X.; Chi, Y.; Zhang, H.; Li, C.; Shi, H.; Joo, M.-K. Hydrothermal synthesis of stable metallic 1T phase WS₂ nanosheets for thermoelectric application. *Nanotechnology* **2018**, *29*, 025705.
31. Yi, J.; She, X.; Song, Y.; Mao, M.; Xia, K.; Xu, Y.; Mo, Z.; Wu, J.; Xu, H.; Li, H. Solvothermal synthesis of metallic 1T-WS₂: A supporting co-catalyst on carbon nitride nanosheets toward photocatalytic hydrogen evolution. *Chem. Eng. J.* **2018**, *335*, 282–289.
32. Fu, Q.; Wang, W.; Yang, L.; Huang, J.; Zhang, J.; Xiang, B. Controllable synthesis of high quality monolayer WS₂ on a SiO₂/Si substrate by chemical vapor deposition. *RSC Adv.* **2015**, *5*, 15795–15799.
33. Zhou, P.; Tanghe, I.; Schiettecatte, P.; Thourhout, D. v.; Hens, Z.; Geiregat, P. Ultrafast carrier dynamics in colloidal WS₂ nanosheets obtained through a hot injection synthesis. *J. Chem. Phys.* **2019**, *151*, 164701.
34. Chen, J.; Shao, K.; Yang, W.; Tang, W.; Zhou, J.; He, Q.; Wu, Y.; Zhang, C.; Li, X.; Yang, X.; et al. Synthesis of wafer-scale monolayer WS₂ crystals toward the application in integrated electronic devices. *ACS Appl. Mater. Interfaces* **2019**, *11*, 19381–19387.
35. Ballif, C.; Regula, M.; Schmid, P.E.; Remskar, M.; Sanjines, R.; Levy, F. Preparation and characterization of highly oriented, photoconducting WS₂ thin films. *Appl. Phys. A* **1996**, *62*, 543–546.
36. Kim, M.-J.; Jeon, S.-J.; Kang, T.W.; Ju, J.-M.; Yim, D.; Kim, H.-I.; Park, J.H.; Kim, J.-H. 2H-WS₂ quantum dots produced by modulating the dimension and phase of 1t-nanosheets for antibody-free optical sensing of neurotransmitters. *ACS Appl. Mater. Interfaces* **2017**, *9*, 12316–12323.
37. Wang, D.; Zhang, Z.; Huang, B.; Zhang, H.; Huang, Z.; Liu, M.; Duan, X. Few-layer WS₂-WSe₂ lateral heterostructures: Influence of the gas precursor selenium/tungsten ratio on the number of layers. *ACS Nano* **2022**, *16*, 1198–1207.
38. Asres, G.A.; Dombovari, A.; Sipola, T.; Puskás, R.; Kukovecz, A.; Kónya, Z.; Popov, A.; Lin, J.-F.; Lorite, G.S.; Mohl, M.; et al. A novel WS₂ nanowire-nanoflake hybrid material synthesized from WO₃ nanowires in sulfur vapor. *Sci. Rep.* **2016**, *6*, 25610.
39. Zhang, L.L.; Tu, J.P.; Wu, H.M.; Yang, Y.Z. WS₂ nanorods prepared by self-transformation process and their tribological properties as additive in base oil. *Mater. Sci. Eng. A* **2007**, *454–455*, 487–491.
40. Mohan, V.V.; Manuraj, M.; Anjana, P.M.; Rakhi, R.B. WS₂ nanoflowers as efficient electrode materials for supercapacitors. *Energy Technol.* **2022**, *10*, 2100976.
41. Sharma, P.; Kumar, A.; Bankuru, S.; Chakraborty, J.; Puravankara, S. Large-scale surfactant-free synthesis of WS₂ nanosheets: An investigation into the detailed reaction chemistry of colloidal precipitation and their application as an anode material for lithium-ion and sodium-ion batteries. *New J. Chem.* **2020**, *44*, 1594–1608.
42. Liu, X.; Xu, J.; Cheng, Z.; Yang, J.; Li, Y. A sensitive acetone sensor based on WS₂/WO₃ nanosheets with p-n heterojunctions. *ACS Appl. Nano Mater.* **2022**, *5*, 12592–12599.
43. Kim, J.-H.; Sakaguchi, I.; Hishita, S.; Ohsawa, T.; Suzuki, T.T.; Saito, N.; Ru-implanted WS₂ nanosheet gas sensors to enhance sensing performance towards CO gas in self-heating mode. *Sens. Actuators B* **2022**, *370*, 132454.

44. Ahmadvand, H.; zad, A.I.; Mohammadpour, R.; H.-Shokouh, S.H.; Asadian, E.; Room temperature and high response ethanol sensor based on two dimensional hybrid nanostructures of -WS₂/GONRs. *Sci. Rep.* **2020**, *10*, 14799.
45. Guang, Q.; Huang, B.; Li, X. Au-decorated WS₂ microflakes based sensors for selective ammonia detection at room temperature. *Chemosensors* **2022**, *10*, 9.
46. Asres, G.A.; Baldoví, J.J.; Dombovari, A.; Järvinen, T.; Lorite, G.S.; Mohl, M.; Shchukarev, A.; Paz, A.P.; Xian, L.; Mikkola, J.-P.; et al. Ultrasensitive H₂S gas sensors based on p-type WS₂ hybrid materials. *Nano Res.* **2018**, *11*, 4215–4224.
47. Gupta, M.; Chaudhary, P.; Singh, A.; Verma, A.; Yadav, D.; Yadav, B.C.; Development of MoO₃-CdO nanoparticles-based sensing device for the detection of harmful acetone levels in our skin and body via nail paint remover. *Sens. Actuators B* **2022**, *368*, 132102.
48. Huang, F.; Jian, J.; Wu, R. Few-layer thick WS₂ nanosheets produced by intercalation/exfoliation route. *J. Mater. Sci.* **2016**, *51*, 10160–10165.
49. Rout, C.S.; Joshi, P.D.; Kashid, R.V.; Joag, D.S.; More, M.A.; Simbeck, A.J.; Washington, M.; Nayak, S.K.; Late, D.J. Superior field emission properties of layered WS₂-RGO nanocomposites. *Sci. Rep.* **2013**, *3*, 3282.
50. Su, P.-G.; Lin-Kuo, S. H₂-gas sensing and discriminating actions of a single-yarn sensor based on a Pd/GO multilayered thin film using FFT. *Anal. Methods* **2020**, *12*, 3537–3544.
51. Chen, L.; Song, Y.; Yu, Q.; Dong, H.; Pan, C.; Wang, D.; Liu, J.; Chen, X. High-performance acetone sensor based on electrospun Tb-doped α -Fe₂O₃ nanotubes. *Ceram. Int.* **2022**, *48*, 26828–26835.
52. Guo, L.; Shen, Z.; Ma, C.; Ma, C.; Wang, J.; Yuan, T. Gas sensor based on MOFs-derived Au-loaded SnO₂ nanosheets for enhanced acetone detection. *J. Alloys Compd.* **2022**, *906*, 164375.
53. Feng, G.; Che, Y.; Wang, S.; Wang, S.; Hu, J.; Xiao, J.; Song, C.; Jiang, L. Sensitivity enhancement of In₂O₃/ZrO₂ composite based acetone gas sensor: A promising collaborative approach of ZrO₂ as the heterojunction and dopant for in-situ grown octahedron-like particles. *Sens. Actuators B* **2022**, *367*, 132087.
54. Zhu, L.-Y.; Yuan, K.; Li, Z.-C.; Miao, X.-Y.; Wang, J.-C.; Sun, S.; Devi, A.; Lu, H.-L. Highly sensitive and stable MEMS acetone sensors based on well-designed α -Fe₂O₃/C mesoporous nanorods. *J. Colloid Interface Sci.* **2022**, *622*, 156–168.
55. Cai, L.; Dong, X.; Wu, G.; Sun, J.; Chen, N.; Wei, H.; Zhu, S.; Tian, Q.; Wang, X.; Jing, Q.; et al. Ultrasensitive acetone gas sensor can distinguish the diabetic state of people and its high performance analysis by first-principles calculation. *Sens. Actuators B* **2022**, *351*, 130863.
56. Zhang, H.-J.; Liu, L.-Z.; Zhang, X.-R.; Zhang, S.; Meng, F.-N. Microwave-assisted solvothermal synthesis of shape-controlled CoFe₂O₄ nanoparticles for acetone sensor. *J. Alloys Compd.* **2019**, *788*, 1103–1112.
57. Bhati, V.S.; Kumar, M.; Banerjee, R. Gas sensing performance of 2D nanomaterials/metal oxide nanocomposites: A review. *J. Mater. Chem. C* **2021**, *9*, 8776–8808.
58. Liang, Y.-C.; Hung, C.-S. Design of hydrothermally derived Fe₂O₃ rods with enhanced dual functionality via sputtering decoration of a thin ZnO coverage layer. *ACS Omega* **2020**, *5*, 16272–16283.
59. Kaur, N.; Singh, M.; Comini, E. One-dimensional nanostructured oxide chemoresistive sensors. *Langmuir* **2020**, *36*, 6326–6344.
60. Siemons, M.; Simon, U. Gas sensing properties of volume-doped CoTiO₃ synthesized via polyol method. *Sens. Actuators B* **2007**, *126*, 595–603.
61. Zhou, X.; Li, X.; Sun, H.; Sun, P.; Liang, X.; Liu, F.; Hu, X.; Lu, G. Nanosheet-assembled ZnFe₂O₄ hollow microspheres for high-sensitive acetone sensor. *ACS Appl. Mater. Interfaces* **2015**, *7*, 15414–1542.
62. Roy, N.; Sinha, R.; Nemade, H.B.; Mandal, T.K. Synthesis of MoS₂-CuO nanocomposite for room temperature acetone sensing application. *J. Alloys Compd.* **2022**, *910*, 164891.
63. Park, S.; Sun, G.-J.; Kim, S.; Lee, S.; Lee, C. UV-enhanced acetone gas sensing of Co₃O₄-decorated ZnS nanorod gas sensors. *Electron. Mater. Lett.* **2015**, *11*, 572–579.
64. Afsar, M.F.; Rafiq, M.A.; Tok, A.I.Y.; Two-dimensional SnS nanoflakes: Synthesis and application to acetone and alcohol sensors. *RSC Adv.* **2017**, *7*, 21556–21566.
65. Giberti, A.; Gaiardo, A.; Fabbri, B.; Gherardi, S.; Guidi, V.; Malagù, C.; Bellutti, P.; Zonta, G.; Casotti, D.; Cruciani, G. Tin(IV) sulfide nanorods as a new gas sensing material. *Sens. Actuators B* **2016**, *223*, 827–833.
66. Mishra, R.K.; Choi, G.J.; Mishra, Y.K.; Kaushik, A.; Sohn, Y.; Lee, S.H.; Gwag, J.S. A highly stable, selective, and high-performance VOC sensor using a SnS₂ nano-lotus structure. *J. Mater. Chem. C* **2021**, *9*, 7713–7725.
67. Tang, H.; Sacco, L.N.; Vollebregt, S.; Ye, H.; Fan, X.; Zhang, G. Recent advances in 2D/nanostructured metal sulfide-based gas sensors: Mechanisms, applications, and perspectives. *J. Mater. Chem. A* **2020**, *8*, 24943–24976.
68. Li, Z.; Li, H.; Wu, Z.; Wang, M.; Luo, J.; Torun, H.; Hu, P.; Yang, C.; Grundmann, M.; Liu, X.; et al. Advances in designs and mechanisms of semiconducting metal oxide nanostructures for high-precision gas sensors operated at room temperature. *Mater. Horiz.* **2019**, *6*, 470–506.
69. Baharuddin, A.A.; Ang, B.C.; Haseeb, A.S.M.A.; Wong, Y.C.; Wong, Y.H. Advances in chemiresistive sensors for acetone gas detection. *Mater. Sci. Semicond. Process.* **2019**, *103*, 104616.
70. Kim, D.H.; Shim, Y.-S.; Jeon, J.-M.; Jeong, H.Y.; Park, S.S.; Kim, Y.-W.; Kim, J.-S.; Lee, J.-H.; Jang, H.W. Vertically ordered hematite nanotube array as an ultrasensitive and rapid response acetone sensor. *ACS Appl. Mater. Interfaces* **2014**, *6*, 14779–14784.
71. Yuan, K.; Wang, C.-Y.; Zhu, L.-Y.; Cao, Q.; Yang, J.-H.; Li, X.-X.; Huang, W.; Wang, Y.-Y.; Lu, H.-L.; Zhang, D.W. Fabrication of a micro-electromechanical system-based acetone gas sensor using CeO₂ nanodot-decorated WO₃ nanowires. *ACS Appl. Mater. Interfaces* **2020**, *12*, 14095–14104.

72. Li, C.; Zhou, H.; Yang, S.; Wei, L.; Han, Z.; Zhang, Y.; Pan, H. Preadsorption of O₂ on the exposed (001) facets of ZnO nanostructures for enhanced sensing of gaseous acetone. *ACS Appl. Nano Mater.* **2019**, *2*, 6144–6151.
73. Sen, S.; Maity, S.; Kundu, S. Fabrication of Fe doped reduced graphene oxide (rGO) decorated WO₃ based low temperature ppm level acetone sensor: Unveiling sensing mechanism by impedance spectroscopy. *Sens. Actuators B* **2022**, *361*, 131706.
74. Cai, Z.; Park, S. Highly selective acetone sensor based on Co₃O₄-decorated porous TiO₂ nanofibers. *J. Alloys Compd.* **2022**, *919*, 165875.
75. Jin, R.; Jiang, Y.; Zhao, L.; Wang, T.; Liu, X.; Liu, F.; Yan, X.; Sun, P.; Lu, G. High sensitivity and low detection limit of acetone sensor based on Ru-doped Co₃O₄ flower-like hollow microspheres. *Sens. Actuators B* **2022**, *363*, 131839.
76. Jin, S.; Wu, D.; Song, W.; Hao, H.; Gao, W.; Yan, S. Superior acetone sensor based on hetero-interface of SnSe₂/SnO₂ quasi core shell nanoparticles for previewing diabetes. *J. Colloid Interface Sci.* **2022**, *621*, 119–130.